

Superconductivity Driven by the Interband Coulomb Interaction and Implications for the Superconducting Mechanism of MgB_2

Masatoshi Imada

Institute for Solid State Physics, University of Tokyo, 5-1-5 Kashiwanoha, Kashiwa, Chiba 277-8581, Japan

(Received February 1, 2008)

Superconducting mechanism mediated by interband exchange Coulomb repulsion is examined in an extended two-band Hubbard models with a wide band crossing the Fermi level and coexisting with a narrower band located at moderately lower energy. We apply newly developed path-integral renormalization group method to reliably calculate pairing correlations. The correlation shows marked enhancement at moderate amplitudes of the exchange Coulomb repulsion taken smaller than the on-site repulsion for the narrower band. The pairing symmetry is s-wave while it has unconventional phases with the opposite sign between the order parameters on the two bands, in agreement with the mean-field prediction. Since the band structure of recently discovered superconductor MgB_2 shares basic similarities with our model, we propose that the present results provide a relevant clue for the understanding of the superconducting mechanism in MgB_2 as well as in this class of multi-band materials with good metallic conduction in the normal state.

KEYWORDS: MgB_2 , pairing mechanism,

Mechanisms of superconductivity have been a long-sort issue since the discovery in 1911 but are still under active studies with aiming at novel mechanisms and searching for materials with higher transition temperatures. In particular, mechanisms driven by the electron-electron interaction in general are widely and intensively studied issue since the discovery of the high- T_c cuprate superconductors,¹⁾ although there exist not many superconducting compounds that have been established as driven by the electron-electron Coulomb interaction. Theoretical studies have intensively focussed on the single-band correlated electron models. In this letter we discuss a different possibility of a high-temperature superconductor by focussing on a wide metallic band coupled by a moderate amplitude of exchange Coulomb interaction to the narrower coexisting band or localized orbitals.

When two different bands or orbitals are located near the Fermi level in metals, several completely different physics may appear. One is the Kondo effect and the heavy fermion behavior where the hybridization and antiferromagnetic spin exchange interaction between localized and itinerant bands play a role for the spin singlet formation and heavily renormalized effective mass of the quasiparticles in lattice. On the other hand, if the hybridization is vanishing or small between the two orbitals, while the exchange Coulomb interaction becomes relatively important, the Hund's rule works efficiently and the atomic high-spin state generically appears, if the level difference between the two atomic orbitals, Γ is relatively small. With this background, the double exchange mechanism works in realizing the ferromagnetic

ground state in metals. The high-spin state appears especially when the ratio between the onsite Coulomb interaction for the lower-level orbital, U , and Γ , namely U/Γ is large. If the interorbital on-site repulsion V is taken into account, this rough estimate of the ratio is replaced with $(U - V)/\Gamma$.

However, if $(U - V)/\Gamma$ becomes relatively small or comparable, the low-spin state may be stabilized and the Hund's rule coupling becomes irrelevant. Near this stabilization point, $(U - V)/\Gamma \leq 1$, another term of the exchange Coulomb interaction between the lower and higher orbitals may work for the stabilized low-spin ground state. This term of the exchange transfers the up and down spin electrons on the same orbital(band) to the other one in pair. In contrast to the ferromagnetism driven by the Hund's rule term, we show that this pair transfer part of the exchange interaction strongly favors the singlet superconducting order in an appropriate range of the parameter space.

In 1963, using the BCS approximation, Kondo³⁾ considered the pairing mechanism assisted by the interband exchange Coulomb interaction between s and d bands for the mechanism of the superconductivity of transition metals. Yamaji^{4,5)} also considered the similar mechanism in a specific condition of two-band Hubbard models. A similar interband mechanism was also examined in strongly correlated models by the authors.⁶⁾

Here, we reexamine the mechanism driven by the exchange Coulomb interaction and show by a newly developed numerical technique that this mechanism works for simple metal compounds mixture with elements with

a localized orbital (or relatively narrow band) located moderately below the Fermi level. Its implication for the mechanism of the superconducting transition in MgB₂ recently discovered by Akimitsu et al.²⁾ above temperature 39K is an important subject of discussions in this letter. We discuss that this mechanism may drive or substantially enhance the superconducting transition of MgB₂.

Our Hamiltonian

$$\mathcal{H} = \mathcal{H}_1 + \mathcal{H}_2 + \mathcal{H}_3 + \mathcal{H}_4 \quad (1)$$

consists of the conduction band $\mathcal{H}_1$ with the wide and narrow bands or localized level part with the on-site Coulomb repulsion terms $\mathcal{H}_2$ and $\mathcal{H}_3$ and with their interorbital Coulomb interaction $\mathcal{H}_4 = \mathcal{H}_{4E} + \mathcal{H}_{4P} + \mathcal{H}_{4V}$:

$$\begin{aligned} \mathcal{H}_1 = & - \sum_{\langle ij \rangle, l, \sigma} t_{lij} (c_{li\sigma}^\dagger c_{lj\sigma} + \text{H.c.}) \\ & - \mu N_1 - (\mu + \Gamma) N_2 \end{aligned} \quad (2)$$

$$\mathcal{H}_2 = U_1 \sum_i n_{1i\uparrow} n_{1i\downarrow} \quad (3)$$

$$\mathcal{H}_3 = U_2 \sum_j n_{2j\uparrow} n_{2j\downarrow} \quad (4)$$

$$\mathcal{H}_{4E} = -J \sum_{i\sigma\sigma'} c_{1i\sigma}^\dagger c_{1i\sigma'} c_{2i\sigma}^\dagger c_{2i\sigma'} \quad (5)$$

$$\mathcal{H}_{4P} = J \sum_{i\sigma\sigma'} (1 - \delta_{\sigma\sigma'}) (c_{1i\sigma'}^\dagger c_{1i\sigma}^\dagger c_{2i\sigma} c_{2i\sigma'} + \text{H.c.}) \quad (6)$$

$$\mathcal{H}_{4V} = V \sum_j n_{1j} n_{2j} \quad (7)$$

$$N \equiv N_1 + N_2, \quad (8)$$

$$N_1 \equiv \sum_{i\sigma} n_{1i\sigma}, \quad (9)$$

$$N_2 \equiv \sum_{l\sigma} n_{2l\sigma}, \quad (10)$$

In Eq.(1-10), the annihilation (creation) operator of the orbital l ($l = 1, 2$) at the site i with the spin σ are represented by $c_{li\sigma}$ ($c_{li\sigma}^\dagger$). In this letter, we assume that U_1 is small by considering a wide metallic band 1 while t_{2ij} is smaller than t_{1ij} .

For the region characterized roughly by $U_2 - V \leq \Gamma - J$, the atomic ground state of the orbital 2 is fully filled singlet. However, when J becomes not too smaller than Γ , the singlet pair can transfer to the conduction band 1 through the term (6) and it generates a charge fluctuation with a singlet cloud around a site of the local orbital 2. In this letter we show that the overlap of such singlet clouds formed around the neighboring atomic orbitals 2 may drive the delocalization of the singlet pair and lead to coherent ground state with the superconducting symmetry breaking. Such formation of itinerant singlet pairs survives, as we show later, when the orbitals 2 form a band through their mutual transfer. If we take the region with the low-spin ground state, the terms (5) and (7) do not play relevant roles and we neglect these terms in the following discussion for simplicity.

Here we first neglect the dispersion of the lower-level band, t_2 in (2) and the Coulomb repulsion U_1 within the conduction band in (3) for simplicity and discuss their effects later. When we take the mean field approximation with the uniform superconducting order parameter

$$\Xi_1 = \frac{J}{N} \sum_i \langle c_{1i\uparrow}^\dagger c_{1i\downarrow}^\dagger \rangle \quad (11)$$

$$\Xi_2 = \frac{J}{N} \sum_i \langle c_{2i\uparrow}^\dagger c_{2i\downarrow}^\dagger \rangle, \quad (12)$$

the selfconsistent equation for the order parameters obtained from the decoupling of the term (6) for $t_{2ij} = 0$ is given by

$$2\Xi_1 = \Xi_2 J / \sqrt{\Xi_2^2 + \Gamma^2} \quad (13)$$

$$\begin{aligned} 2\Xi_2 = & -U_2 \Xi_2 / \sqrt{\Xi_2^2 + \Gamma^2} \\ & + \Xi_1 J \int_{-W_1/2}^{W_1/2} d\epsilon \frac{D_1(\epsilon)}{\sqrt{\epsilon^2 + \Xi_1^2}} \end{aligned} \quad (14)$$

where the density of states of the conduction band 1 is $D_1(\epsilon)$ with the dispersion $\epsilon(k) = \sum_{i,j} t_{1ij} \exp(ik(r_i - r_j)) - \mu$ and W_1 is the bandwidth of the band 1 in proportion to $1/t_1$. When the density of states is replaced with the rectangular constant one for the conduction band for simplicity, namely, $D_1(\epsilon) = 1/W_1$, the selfconsistent solution at temperature $T = 0$ in the weak coupling BCS limit is given by

$$\Xi_1 \sim W_1 \exp[-\frac{2W_1}{J^2} (U_2 + \Gamma/x)]. \quad (15)$$

Here x denotes the number of the orbital 2 in a unit cell and if the orbital 2 forms a band through nonzero t_{2ij} , basically x may be replaced with the integrated density of states of this narrower band with the width W_2 .

An important point of this pairing mechanism is that the prefactor in Eq.(15) is determined from the bare bandwidth of the wide band 1. In addition, the argument of the exponential function may have order unity when we may assume that J, U, Γ , and W_1 would have comparable values. This may necessarily requires the consideration in a strong coupling region. However, here we took a BCS weak-coupling approach as a starting

point and by assuming that W_1 is the largest parameter among the energy scales. The strong coupling correction is left for further studies.

Even more important point of this mechanism is that the pairing order parameters on the bands 1 and 2 have the opposite sign, namely $\sum_{i,j} \langle c_{1i\sigma}^\dagger c_{1i-\sigma}^\dagger c_{2j-\sigma} c_{2j\sigma} \rangle < 0$ because the pairing is mediated by *repulsive* interband exchange interaction. This anisotropy may enable us to distinguish the present pairing mechanism from that of the conventional phonon-mediated BCS theory.

This weak coupling mean-field picture is complemented by numerical study of the Hamiltonian (1) in the following. We employ recently developed path-integral renormalization group method⁷⁾ to perform a controlled calculation in the ground state. Since our basic picture applies to any type of lattice structure, we first employ a numerically feasible square lattice for simplicity and introduce orbital 2 by replacing a fraction of the lattice points (denoted by B in Fig. 1) regularly and assign orbital 1 to the rest of the lattice sites (denoted by A in Fig. 1). We have introduced the B sites periodically in x and y directions with the period l_B . The wide band 1 is formed from the nearest neighbor transfers t_1 between the sites A while the narrower band is formed from the nearest neighbor transfer t_2 between the sites B. The unit cell of this lattice becomes $l_B \times l_b$ and it causes a folding of the Brillouin zone with multi-band structure instead of the band 1. However it does not alter our basic argument especially near the Fermi level. The transfer between A and B sites is switched off. We also introduce an on-site Coulomb repulsion U_2 for the sites B (on the band 2) while the onsite Coulomb interaction for the free-electron like band 1, U_1 is taken small. The exchange Coulomb interaction J given by Eq.(6) is introduced between nearest neighbor A and B sites. The atomic level difference between the sites A and B is Γ .

We have calculated the pairing correlation between the A and B sites as well as other combinations of the pairing between two A sites and between two B sites. Here, the pairing correlation is defined by

$$P_{lm}(i, j) = \langle c_{li\sigma}^\dagger c_{li-\sigma}^\dagger c_{mj-\sigma} c_{mj\sigma} \rangle \quad (16)$$

We fix $\Gamma/t_1 = U_2/t_1 = 3$, $t_2/t_1 = 0.3$ and $U_1/t_1 = 0.2$ where the largest effect of J is expected in the region of comparable U_2 and Γ as we discussed above. In a realistic situation, J has to be smaller than U_2 and we show J dependence of the pairing correlation in Fig. 2.

Figure 2 shows the amplitude of the pairing correlation between a site on the A sublattice (with the coordinate (0,0)) and all the other sites (i, j) including A and B for a 6 by 6 square lattice with the periodic boundary condition, $l_B = 3$ and the electron density $n = 0.5$ per site. The distance between (0,0) and (i, j) is given by r . The interband pairing correlations P_{12} has mostly negative values as we expect. The overall correlation clearly shows marked enhancement for J

roughly larger than $U_2/2$. The enhancement is seen in a comparison with a practically noninteracting case with $U_1/t_1 = U_2/t_1 = J_1/t_1 = 0.01$ with the same band parameters $t_2/t_1 = 0.3$ and $\Gamma/t_1 = 3$ as before. This implies that the pairing may be driven in a realistic range of the parameters when a wide band is coupled by the exchange Coulomb interaction to a narrower band and the hybridization between these two bands is vanishing.

The result also shows that the short-ranged part of the pairing correlation becomes larger simply with the increase in J while the longer-ranged part has a maximum at an intermediate value of J below U_2 . This is a natural consequence because the strongly coupled singlet is tightly formed at larger J . It bears more local character and an effective hopping amplitude of the singlet becomes smaller when J becomes too large as is seen for an unrealistic choice of $J/t_1 = 5 > U_2/J$.

Although the size scaling is difficult for the moment, similar enhancements are also seen in larger lattice sizes. When the electron correlations become small, the scale of the enhancements becomes small accordingly while the enhancement itself seems to universally exist if the ratios of U_1, J and Γ are retained. The overall feature of the enhancement is in qualitative agreement with that expected from the parameter dependence of the mean-field result Eq.(15).

We next discuss the implication of this result for the mechanism of superconductivity discovered in MgB₂. The crystal of MgB₂ has so called AlB₂-type hexagonal structure with an alternate stacking of Mg and B honeycomb layers. The band structure^{8,9,10)} suggests that degenerate bands with two-dimensional anisotropy are formed from B $2p_\sigma$ band and its bonding part crosses the Fermi level near the top of the band. In the band structure calculations, the center of the B $2p_\sigma$ bonding band is 1-2 eV below the Fermi level and two cylindrical hole Fermi surface appears around the axis through Γ to A points due to the bandwidth of the order of 4 eV. A rather separate free-electron like band also crosses the Fermi level, which is formed from the hybridization of Mg sp and B p_z bands and has a bandwidth larger than 10 eV. The Mg sp band is expected to have a rather small electron correlation while B p_σ band may have a moderate correlation due to dominant p character confined in the two-dimensional honeycomb layer. Because of their symmetries, these two bands do not seem to be appreciably hybridized and are clearly separated near the Fermi level. This band structure is essentially similar to our model with the band 1 (corresponding to Mg sp -B p_z) and the band 2 (B- p_σ). Although the amplitude of the electron correlation is not well known in this compound, the choice of the parameters in our calculations in comparison with plausible values of parameters for MgB₂ does not seem to be unrealistic and provides a good starting point in the present stage. Our calculated result shows that the pairing enhancement becomes optimized

for comparable U and Γ while it is suppressed, for example, for too large Γ . This is consistent with the fact that AlB_2 does not show superconductivity because the $B p_\sigma$ level is deep in AlB_2 . On the other hand, if Γ becomes too small, the Hund's rule coupling starts working and the ferromagnetic state becomes more stable. In a series of the binary compounds of boronides, we expect that the ferromagnetic and superconducting phase may appear rather close each other with competitions.

In this compound, phonon modes of Boron oscillation may have relatively high frequencies and may take a strong electron-phonon coupling which may support the phonon-mediated conventional pairing.^{10,11)} Our proposal gives an alternative possibility or may play a complementary role. In comparison with the phonon mechanism, our mechanism contains a specific prediction where the phases of the order parameter on the $B p_\sigma$ band and $B p_z$ bands hybridized with $\text{Mg } sp$ should have the opposite sign. This is a crucial test for the role of the interband Coulomb exchange as a driving force of the superconductivity. This may be tested in a carefully designed junction to pick up the opposite phase. Although the pairing symmetry is s-wave as supported also experimentally¹²⁾, our theory suggests that it is not a simple BCS isotropic pairing.

In summary, we have analyzed a superconducting mechanism mediated by the interband Coulomb exchange repulsion. The numerical simulation results suggest enhancements of pairing for the combination of wide and narrower bands crossing the Fermi level without mutual hybridization but with a moderate amplitude of the exchange Coulomb interaction. We have proposed that this mechanism may be relevant to the occurrence of superconductivity recently discovered in MgB_2 .

Acknowledgements

The author would like to thank J. Akimitsu for fruitful discussions on detailed experimental results and presenting the data to the author in prior to the publication. The author also thanks H. Harima for illuminating discussions and data for the band structure. The fruitful conversation with K. Kusakabe is also acknowledged. This work is supported by a Grant-in-Aid for "Research for the Future" Program from the Japan Society for the Promotion of Science under the project JSPS-RFTF97P01103.

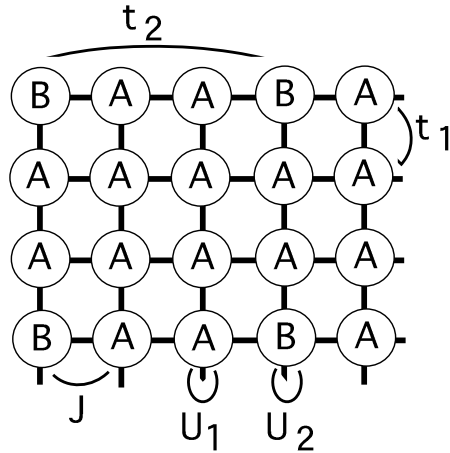


Fig. 1. The lattice structure employed in our numerical simulation.

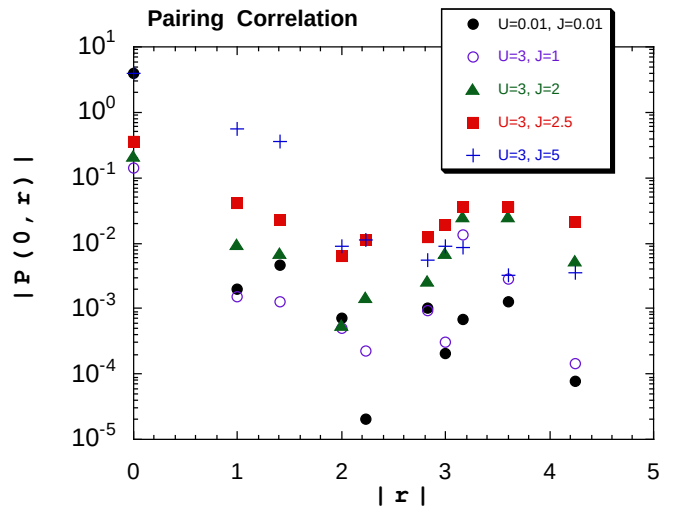


Fig. 2. The absolute amplitude of the pairing correlation $|P|$ as a function of distance for an extended two-band Hubbard model. The choices of J are $J = 1, 2, 2.5$ and 5 . These results are compared with the practically noninteracting system with $U_1/t_1 = U_2/t_1 = J/t_1 = 0.01$. The pairing correlation shows marked enhancement in a range of the interband exchange Coulomb interaction J . See the text for details.

- [1] J. G. Bednorz and K.A. Muller: *Z. Phys.* **64** (1986) 189.
- [2] J. Akimitsu, private communication and to appear in *Nature*.
- [3] J. Kondo, *Prog. Theor. Phys.* (1963) **29** 1.
- [4] K. Yamaji, *J. Phys. Soc. Jpn.* **59** (1990) 677.
- [5] K. Yamaji, *Physica* **222C** **64** (1994) 349.
- [6] M. Imada and M. Kohno, *Phys. Rev. Lett.* **84** (2000) 143.
- [7] M. Imada and T. Kashima, *J. Phys. Soc. Jpn.* **59** (1990) 677.
- [8] H. Harima: unpublished
- [9] A.L.Ivanovskii and N.I. Medvedeva: *Russian J. Inorganic Chemistry*, **45** (2000) 1335.

- [10] J. Kortus, I.I.Mazin, K.D. Belashchenko, V.P. Antropov and L.L. Boyer: *cond-mat/0101446*
- [11] J.M. An and W.E. Pickett: *cond-mat/0102391*
- [12] H. Kotegawa, K. Ishida, Y. Kitaoka, T. Muranaka and J. Akimitsu: *cond-mat/0102334*.